


N.I.

WANL-PR-(Q)-014
NASA-CR-72306

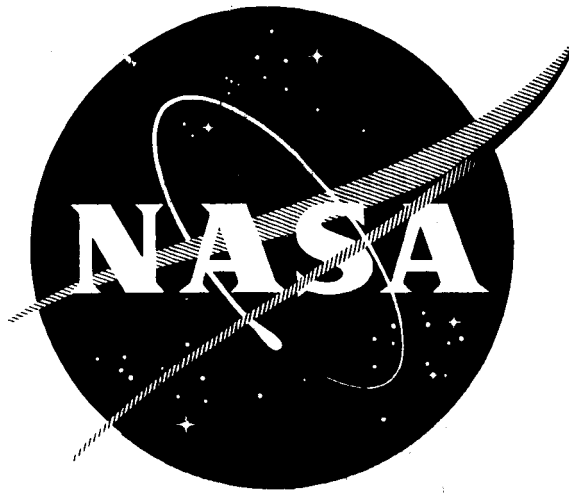

DEVELOPMENT OF DISPERSION STRENGTHENED TANTALUM BASE ALLOY

Thirteenth Quarterly Report

by

R. W. Buckman and R. C. Goodspeed

prepared for

National Aeronautics and Space Administration

Lewis Research Center

Space Power Systems Division

Under Contract (NAS 3-2542)



ASTRONUCLEAR LABORATORY

WESTINGHOUSE ELECTRIC CORPORATION

N68-13630

(ACCESSION NUMBER)

(THRU)

(PAGES)

(CODE)

CR-72306

(NASA CR OR TMX OR AD NUMBER)

(CATEGORY)

GPO PRICE \$

CFSTI PRICE(S) \$

Har copy (HC)

Microfiche (MF)

ff 653 July 85

NOTICE

This report was prepared as an account of Government-sponsored work. Neither the United States nor the National Aeronautics and Space Administration (NASA), nor any person acting on behalf of NASA:

- A) Makes any warranty or representation, expressed or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately-owned rights; or
- B) Assumes any liabilities with respect to the use of, or for damages resulting from the use of any information, apparatus, method or process disclosed in this report.

As used above, "person acting on behalf of NASA" includes any employee or contractor of NASA, or employee of such contractor, to the extent that such employee or contractor of NASA or employee of such contractor prepares, disseminates, or provides access to, any information pursuant to his employment or contract with NASA, or his employment with such contractor.

Copies of this report can be obtained from:

National Aeronautics & Space Administration
Office of Scientific and Technical Information
Washington 25, D. C.
Attention: AFSS-A

001127

DEVELOPMENT OF DISPERSION STRENGTHENED
TANTALUM BASE ALLOY

by

R. W. Buckman, Jr.

and

R. C. Goodspeed

THIRTEENTH QUARTERLY PROGRESS REPORT

Covering the Period

November 20, 1966 - February 20, 1967

Prepared For

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION
Contract NAS 3-2542

Technical Management
Paul E. Moorhead
NASA-Lewis Research Center
Space Power Systems Division

Astronuclear Laboratory
Westinghouse Electric Corporation
Pittsburgh 36, Pa.

PRECEDING PAGE BLANK NOT FILMED.

ABSTRACT

Development of dispersion strengthened tantalum base alloys for use in advanced space power systems continued as the evaluation of Ta-8W-1Re-1Hf (ASTAR-811) and Ta-7W-1Re-1Hf-0.012C-0.012N (ASTAR-811CN) sheet material was essentially completed. Tensile properties of TIG welded sheet specimens of both alloys were determined over the temperature range of -320 to 2600°F . One hour post weld anneals at temperatures ranging from 1800 to 2600°F resulted in an increase in the ductile-brittle transition temperature of TIG welded ASTAR-811CN, while the transition temperature of TIG welded ASTAR-811 remained below -320°F . Phase identification studies on ASTAR-811CN indicated that the HCP tantalum dimetal carbide is the precipitate which occurs during processing to 0.04 inch sheet and short time anneals. The FCC carbonitride phase occurs at the expense of the dimetal carbide during longer (≥ 16 hours) anneals at temperatures of about 2400°F and higher. The scope of work this period was expanded to include an investigation of the effect of grain size and annealing temperatures on the creep properties of ASTAR-811, ASTAR-811CN, and ASTAR-811C (Ta-8W-1Re-0.7Hf-0.025C). Grain size data were obtained on these alloys as a function of annealing time and temperature.

TABLE OF CONTENTS

	<u>Page No.</u>
I. INTRODUCTION	1
II. PROGRAM STATUS	2
A. EFFECT OF THERMAL TREATMENT ON CREEP BEHAVIOR	2
B. INTERSTITIAL ELEMENT LOSSES DURING VACUUM HEAT TREATMENT	7
C. WELDABILITY	11
D. MECHANICAL PROPERTIES	20
III. FUTURE WORK	29
IV. REFERENCES	31

LIST OF FIGURES

	<u>Page No.</u>
1. Grain Size of ASTAR-811, ASTAR-811C, and ASTAR-811CN as a Function of Annealing Time and Temperature	5
2. Parabolic Rate Constant for Grain Growth of ASTAR-811, ASTAR-811C, and ASTAR-811CN as a Function of Reciprocal Temperature	6
3. Carbon and Nitrogen Losses in Unwrapped and Wrapped ASTAR-811CN as a Function of Time at 2100°C	9
4. Total Interstitial Losses in Unwrapped and Wrapped ASTAR-811CN as a Function of Time at 2100°C	10
5. Ductile-Brittle Transition Temperature Test Results for Post (TIG) Weld Annealed ASTAR-811CN	13
6. Results of Hardness Traverses Across As-Welded Specimens of ASTAR-811 and ASTAR-811CN	15
7. Representative Microstructures of TIG Welded ASTAR-811	16
8. Microstructure of Weld Zone/Heat Affected Zone Interface in TIG Welded ASTAR-811C Specimen After 1 Hr. Post Weld Anneal at 1200°C	17
9. Microstructures of TIG Welded ASTAR-811CN Specimens After 1 Hr. Post Weld Anneals at Various Temperatures	18
10. Creep Properties of ASTAR Tantalum Alloys	25
11. Aging Behavior of ASTAR-811CN	30

LIST OF TABLES

	<u>Page No.</u>
1. Effect of Annealing Temperature and Annealing Time on the Grain Size of ASTAR-811, ASTAR-811C and ASTAR-811CN	3
2. Chemical Analyses of Unwrapped and Wrapped ASTAR-811CN as a Function of Time at 2100°C (3810°F)	8
3. Ductile-Brittle Transition Temperature of Post (TIG) Weld Annealed NASV-23	12
4A. Tensile Properties of TIG Welded ASTAR-811, ASTAR-811C and ASTAR-811CN	21
4B. Tensile Properties of TIG Welded ASTAR-811 and ASTAR-811CN	22
5. Creep Properties of ASTAR-811 and ASTAR-811CN	24
6. X-ray Diffraction Analyses of Various ASTAR-811CN Bulk Extracted Residues	27
7. X-ray Diffraction Analyses of Phases Extracted from ASTAR-811CN Specimens Annealed for 1 Hr. at 1650°C and Aged for 1 and 16 Hrs. at 1090, 1200, 1315, and 1425°C	28

I. INTRODUCTION

This, the thirteenth quarterly progress report on the NASA-sponsored program, "Development of Dispersion Strengthened Tantalum Base Alloys" describes the work accomplished during the period November 20, 1966 to February 20, 1967. The work was performed under Contract NAS 3-2542.

The primary objective of the current phase of this program is the processing and evaluation of 0.04 inch sheet of three compositions which were melted as 60-pound, 4-inch diameter ingots. The compositions were selected for potential sheet and tubing applications on the basis of weldability, creep resistance, and fabricating characteristics.

Prior to this quarterly period, several promising tantalum alloy compositions were developed which exhibited a good combination of creep resistance, weldability, and fabricability.⁽¹⁾ The three compositions selected for scale up are:

ASTAR-811	Ta-8W-1Re-1Hf
ASTAR-811C	Ta-8W-1Re-1Hf-0.025C
ASTAR-811CN	Ta-7W-1Re-1Hf-0.012C-0.012N

These compositions were consumable electrode double vacuum arc melted as 60-pound, 4-inch diameter ingots, which were subsequently processed to 0.04-inch sheet by a combination of forging and rolling. Evaluation of composition Ta-8W-1Re-1Hf-0.025C (ASTAR-811C) has been essentially completed,⁽²⁾ and evaluation of the remaining two compositions Ta-8W-1Re-1Hf (ASTAR-811) and Ta-7W-1Re-1Hf-0.012C-0.012N (ASTAR-811CN), initiated.⁽³⁾

During this quarterly period the evaluation of weldability, tensile properties, and creep resistance of the Ta-8W-1Re-1Hf (ASTAR-811) and Ta-7W-1Re-1Hf-0.012C-0.012N (ASTAR-811CN) was essentially completed. The scope of the contract was also expanded to include an investigation of the effect of grain size on the creep properties of all three scale-up alloys. To date grain size data has been obtained as a function of annealing time and temperature.

II. PROGRAM STATUS

A. EFFECT OF THERMAL TREATMENT ON CREEP BEHAVIOR

The scope of work was changed to include a limited investigation on the effect of final annealing treatment on the creep behavior of the ASTAR-811, ASTAR-811C, and ASTAR-811CN compositions. Prior work⁽⁴⁾ on ASTAR-811C (Ta-8W-1Re-1Hf-0.025C) has shown that creep behavior is strongly influenced by the final annealing temperature. Increasing the final annealing temperature from 1650°C to 2000°C resulted in a 50% reduction in creep rate. However, the average grain diameter increased from 0.03 mm to 0.18 mm as the 1 hour annealing temperature was increased from 1650°C to 2000°C. In addition there was also a significant change in the precipitate morphology as the annealing temperature was increased.⁽⁴⁾ Thus it is important to identify the factors contributing to the observed improvement in creep behavior. A series of specimens will be annealed over the temperature range of 1800-2100°C for a time sufficient to produce a final grain size of 0.03 mm, the resulting grain size achieved after the standard final annealing treatment, i. e., 1 hour at 1650°C. The specimens will then be creep tested at 2400°F under an applied stress of 15,000 psi.

During this period, 0.04-inch thick sheet specimens of all three ASTAR compositions were annealed at 1800, 1900, 2000, and 2100°C (3270, 3450, 3630, and 3810°F) for 30, 300, and 900 seconds. The 0.04-inch sheet from which the specimens were taken had been reduced 85% by cold rolling. The average grain diameter determined by the line intercept method and room temperature hardness data are recorded in Table 1. The annealing sequence consisted of slowly heating the furnace to 1200°C while maintaining the chamber pressure at $\leq 1 \times 10^{-5}$ torr and then heating to the desired temperature as rapidly as possible. Time at temperature was recorded from when the specimen reached a temperature within 50°C of the test temperature. After the specified time at temperature the furnace was shut off and the chamber was back-filled with helium gas to accelerate cooling of the specimens. All specimens were heat treated bare. From these results the heat treatments selected to produce a grain size of 0.03 mm are

TABLE 1 - Effect of Annealing Temperature and Annealing Time on the Grain Size of ASTAR-811, ASTAR-811C, and ASTAR-811CN

Composition	Annealing Time (min.)	Grain Size (in mm) and Hardness ⁽¹⁾ for Temperatures, °C/°F									
		1800		1900		2000		2100			
		GS	DPH	GS	DPH	GS	DPH	GS	DPH	GS	DPH
ASTAR-811 (Ta-8W-1Re-1Hf)	1/2	0.016	196	0.024	199	0.029	202	0.042	199		
	5	0.024	200	0.038	196	0.077	197	0.098	195		
	15	0.045	181	0.079	194	0.118	182	0.186	197		
ASTAR-811C (Ta-8W-1Re-0.7Hf-0.025C)	1/2	0.016	263	0.021	262	0.033	270	0.038	254		
	5	0.026	267	0.030	258	0.067	268	0.093	256		
	15	0.045	271	0.065	251	0.100	281	0.178	255		
ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N)	1/2	0.013	287	--	--	0.031	305	--	--		
	5	0.026	294	--	--	0.067	288	--	--		
	15	0.039	297	--	--	0.107	272	--	--		

(1) DPH, 30 Kg load.

as follows:

10 minutes at 1800°C/3270°F

5 minutes at 1900°C/3450°F

30 seconds at 2000°C/3630°F

It has been shown that under isothermal conditions, the grain size (D) varies with time (t) according to the following expression:



$$D^2 = K \gamma V t$$

where the surface energy of the boundary (γ) is the driving force for boundary migration. K is a rate constant and V is the grain atomic volume. Thus at a given temperature, the grain size is proportional to the square root of time. The grain size data in Table 1 when plotted as a function of time (see Figure 1) result in a good linear fit. The slope of this curve $\frac{\partial D}{\partial t^{1/2}}$ is equal to \sqrt{K} , the parabolic rate constant which varies with temperature according to the familiar Arrhenius rate equation;

$$K = K_0 \exp^{-Q/RT}$$

where Q is the activation energy, T is absolute temperature, R is the gas constant, and K_0 a proportionality constant. Thus the activation energy for grain growth can be calculated from the slope of the curve D^2/t vs $1/T$. From the D^2/t vs $1/T$ plot in Figure 2, a value of Q of 92 kcal/mole was determined. The activation energy for the self diffusion of tantalum is reported to be 110 kcal/mole⁽⁵⁾ and it would be expected that the activation energy for grain boundary migration would be less than one-half this value. Thus the value of 92 kcal/mole determined for these tantalum alloys appears to be higher than would normally be expected. The explanation for this apparent high value is not evident.

The grain growth behavior of all three tantalum compositions was identical over the range of test temperatures studied. This would be expected for the ASTAR-811 and ASTAR-811CN since at 1800°C, the solvus for the 0.012C and 0.012N has been exceeded. However, the carbon solvus for the ASTAR-811C which contains 0.025% is not exceeded until heating

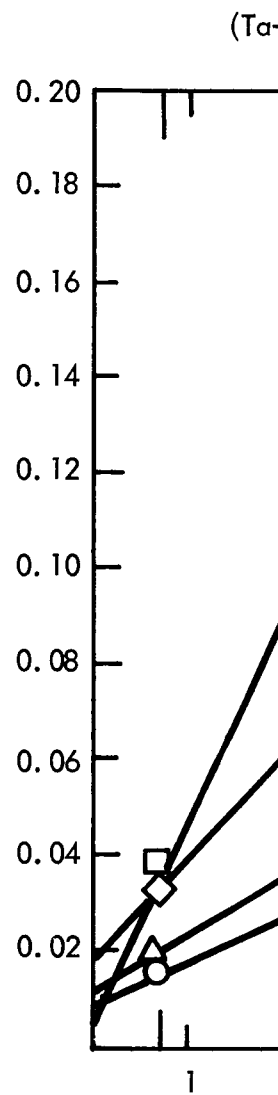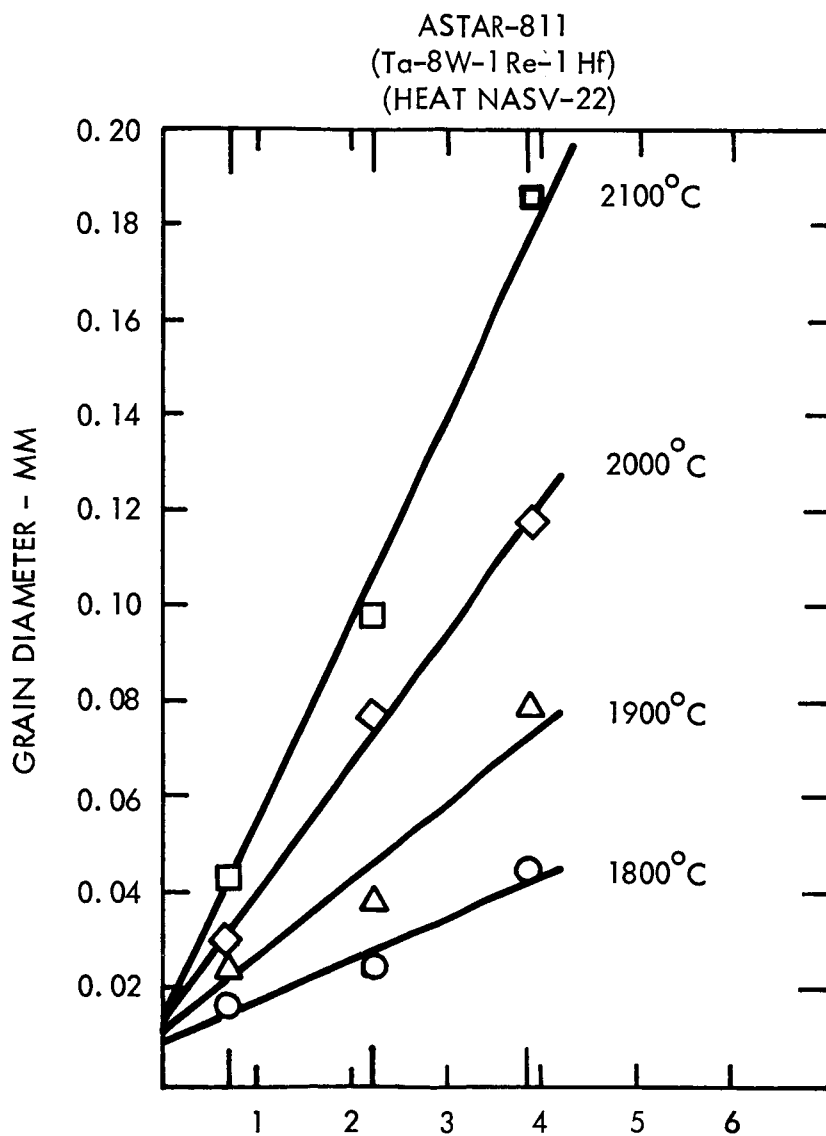

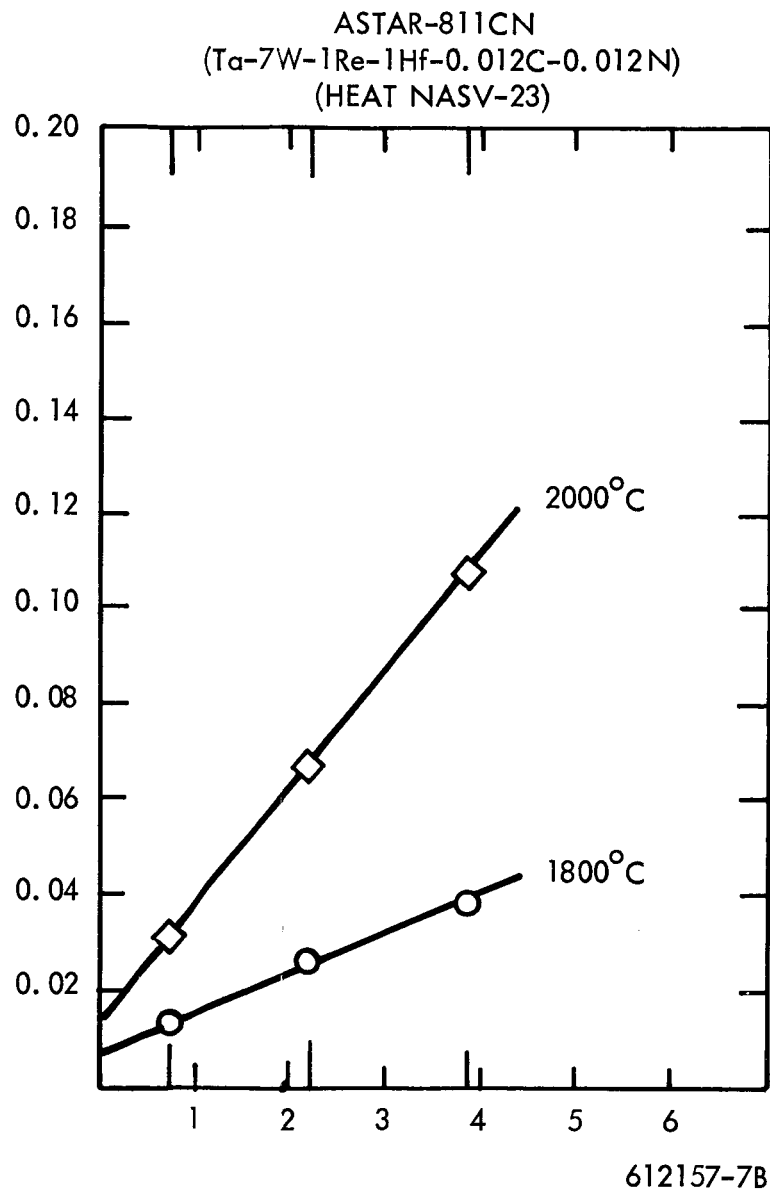
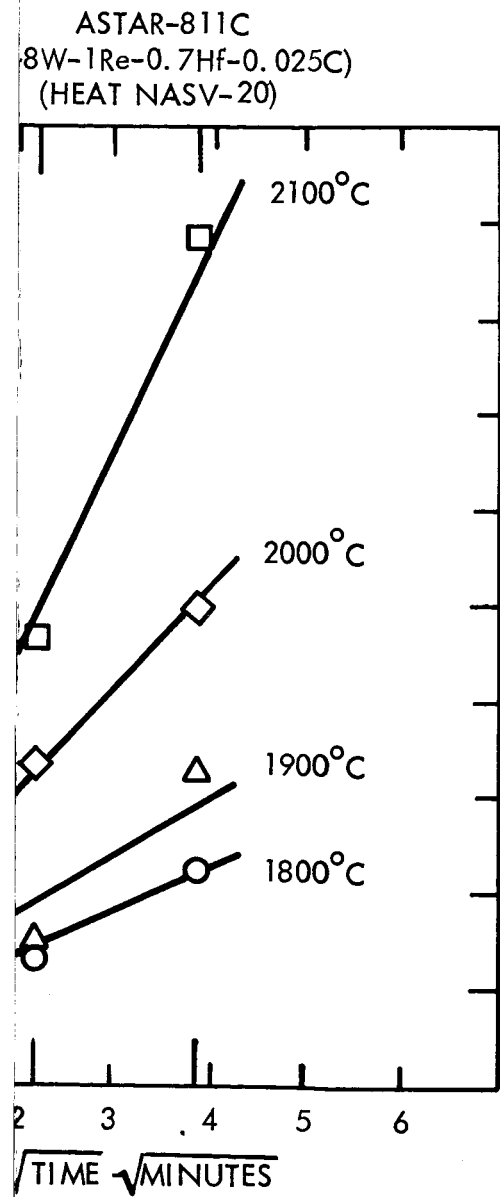


FIGURE 1 - Grain Size of ASTAR-811, ASTAR-811C, and ASTAR-811CN as a Function of Annealing Time and Temperature

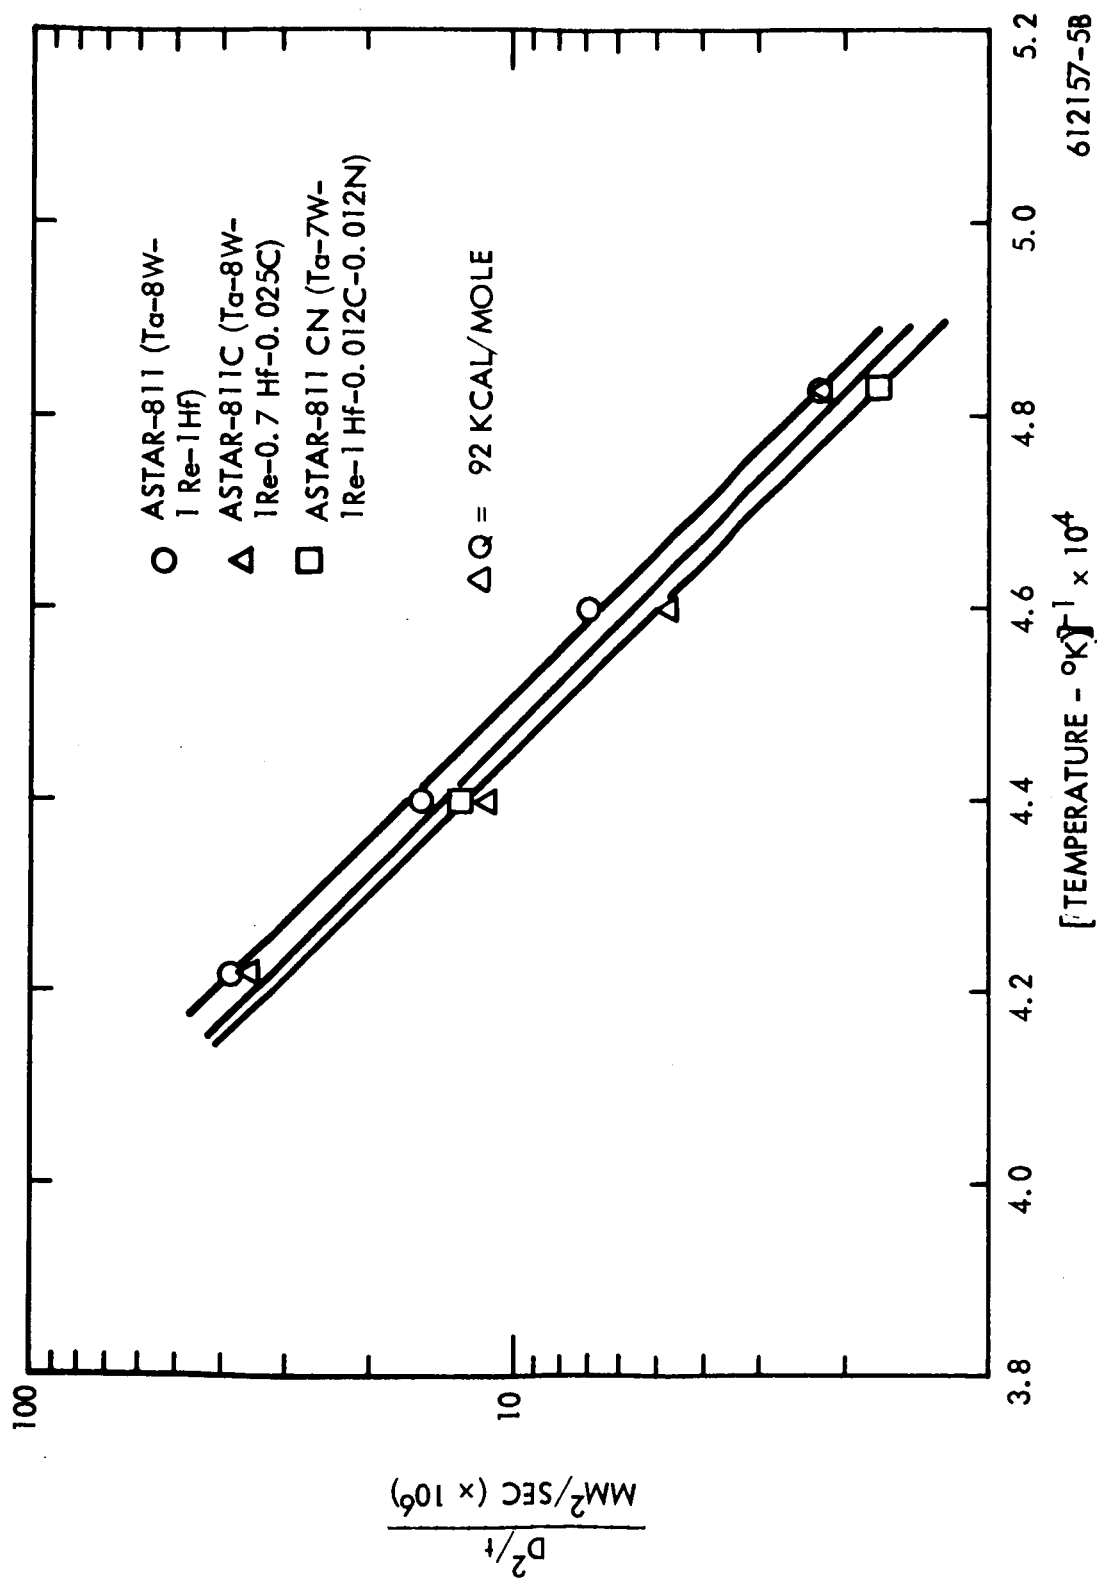


FIGURE 2 - Parabolic Rate Constant for Grain Growth of ASTAR-811, ASTAR-811C, and ASTAR-811CN as a Function of Reciprocal Temperature

above 1900°C. Thus it can be concluded that the carbide particles present at 1800°C do not inhibit grain boundary migration.

B. INTERSTITIAL ELEMENT LOSSES DURING VACUUM HEAT TREATMENT

The carbide and nitride phases in the tantalum alloy matrix have appeared stable for long time periods over the temperature range of 1800-2600°F when exposed at pressures of $\leq 1 \times 10^{-8}$ torr.⁽⁶⁾ However, as discussed previously, the optimum creep characteristics are achieved by using final annealing treatments in the 3200-3600°F temperature range. Current industry wide practice for high temperature vacuum heat treatment is to use unbaked, polymer sealed systems operating at $10^{-5} - 10^{-4}$ torr. Most heat treatment specifications also require Ta, Cb, or Cb-1Zr foil wrapping of the work piece as a barrier to contamination during the annealing cycle. Decarburization of a carbon containing tantalum alloy at 1×10^{-5} torr at >2000°C was reported early in this investigation.⁽⁷⁾ It is assumed that the decarburization is via the methane and/or CO reactions similar to that reported for decarburization of molybdenum alloys. It was also shown that wrapping the sample with pure tantalum foil resulted in a greater carbon loss. It is assumed that the foil acts as a sink and that the rate of carbon transfer across the foil interface is faster than the carbon loss due to reaction with the residual H_2 , H_2O present in the vacuum chamber atmosphere at 1×10^{-5} torr.

Additional vacuum annealing tests were made during the report period on the carbonitride strengthened composition ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N). Sheet specimens, 0.04-inch thick, bare and wrapped with tantalum foil, were exposed for 5, 30, and 60 minutes at 2100°C (3810°F). After heat treatment, the samples were then analyzed for carbon and nitrogen content. The analytical results are recorded in Table 2 and graphically illustrated in Figures 3 and 4. Significant carbon and nitrogen losses have occurred during this annealing treatment and confirm the losses observed previously when annealing this composition at 2000°C and above.⁽³⁾ The use of a foil wrapping, while reducing the possibility of oxygen contamination, acts as a sink for carbon. The nitrogen loss is assumed to be by degassing and the foil wrapping appears to retard the rate at which it occurs.

TABLE 2 - Chemical Analyses of Unwrapped and Wrapped^(a) ASTAR-811CN
(Ta-7W-1Re-1Hf-0.012C-0.012N) as a Function of Time at
2100°C/3810°F and 1×10^{-5} Torr in Oil Diffusion Pumped Vacuum System

Condition ^(b)	Time (min.)	Carbon Content (ppm)	% Carbon Lost	Nitrogen Content (ppm)	% Nitrogen Lost	Total Interstitials Lost	
						ppm	(%)
Unwrapped	5	96	20	64	47	80	33.5
	30	64	47	49	59	127	53
	60	55	54	31	74	154	64
Wrapped ^(a)	5	72	40	113	6	55	23
	30	82	32	70	42	88	37
	60	47	61	64	47	129	54

(a) Specimens wrapped tightly in pure tantalum foil.

(b) Initial carbon and nitrogen content 120 ppm.

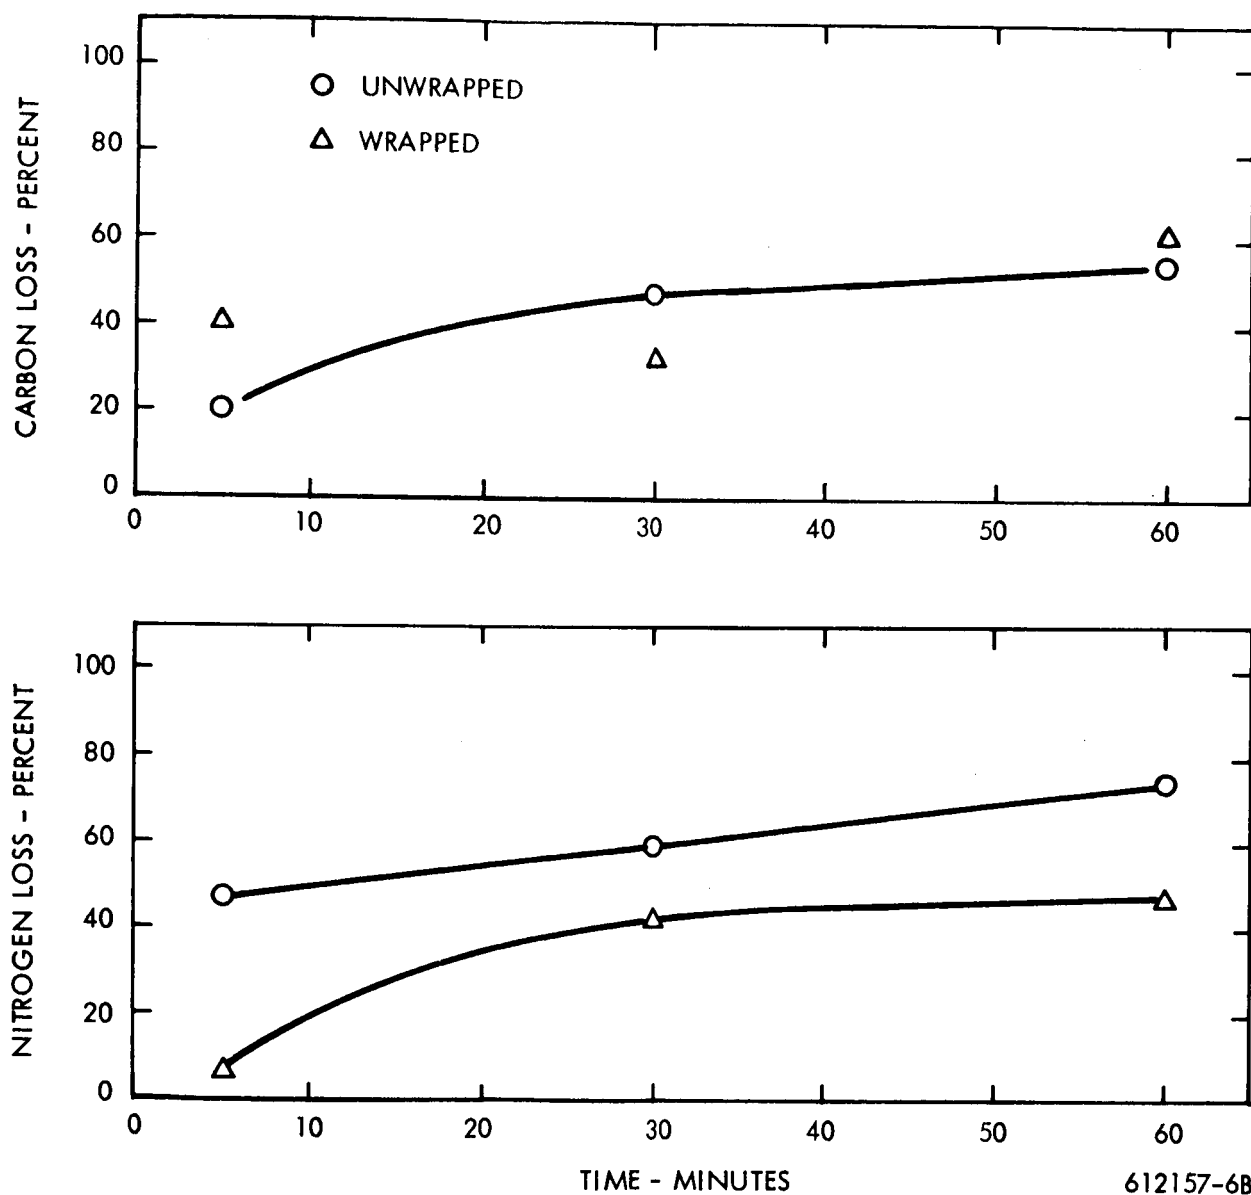


FIGURE 3 - Carbon and Nitrogen Losses in Unwrapped and Wrapped ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N) as a Function of Time at 2100°C/3810°F and 1×10^{-5} Torr in Oil Diffusion Pumped System

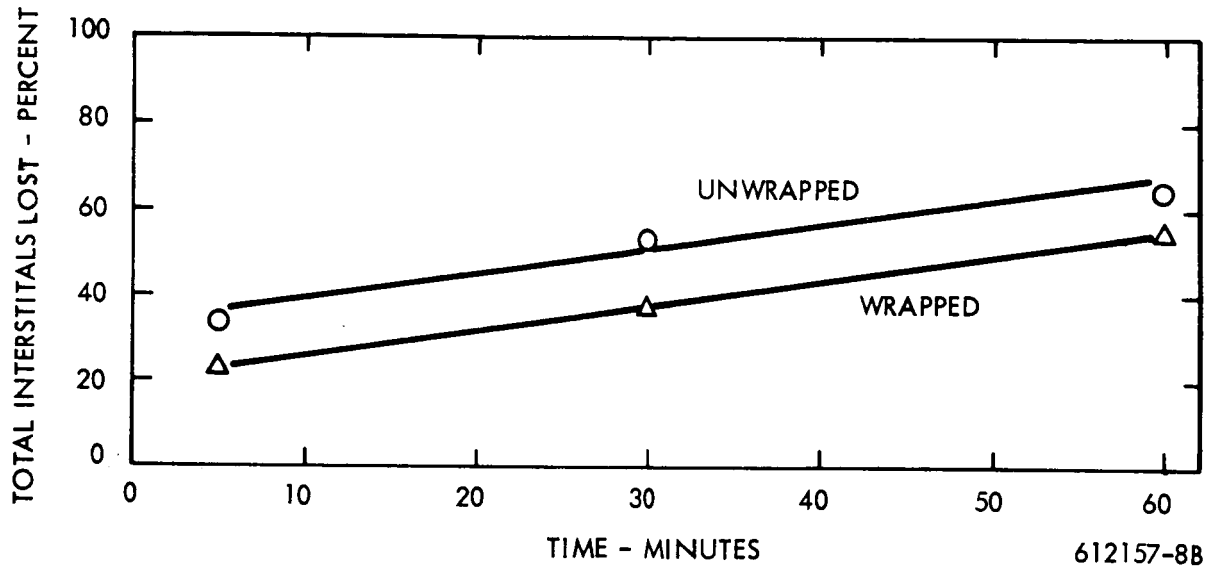


FIGURE 4 - Total Interstitial Losses in Unwrapped and Wrapped ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N) as a Function of Time at 2100°C/3810°F and 1×10^{-5} Torr in Oil Diffusion Pumped System

These tests are very preliminary in nature and more detailed work is beyond the scope of this program. But certain obvious implications arise if refractory metal alloys strengthened with carbide and/or nitride dispersions are to be utilized to the fullest. High temperature vacuum annealing treatments on alloys of the type which have been developed during this investigation may have to be accomplished in bakeable ultra-high vacuum systems to prevent carbon loss and with a controlled nitrogen partial pressure to prevent nitrogen loss. There is no doubt that a general improvement in the current state-of-the-art of vacuum annealing as practiced by the industry will have to be advanced in order to ensure that interstitial composition does not change during the required annealing treatment. This advancement will necessarily include the development of large bakeable ultra high vacuum furnaces capable of operation at up to approximately 4000°F.

C. WELDABILITY

The effect of post weld annealing on the ductile-brittle transition temperature was determined on 0.04-inch sheet of ASTAR-811 and ASTAR-811CN which had been annealed for 1 hour at 1650°C and then TIG welded. Bead-on-plate type welds with 100% penetration were tested in bending over a 1t bend radius with the weld bead transverse to the bend axis. After welding specimens were annealed for 1 hour at 980, 1200, and 1425°C (1800, 2200, and 2600°F). The data obtained are recorded in Table 3. The ductile-brittle transition temperature of the solid solution alloy ASTAR-811 was less than -320°F as-TIG welded and did not change as a result of post-weld annealing. However, the transition temperature of the as-TIG welded ASTAR-811CN increased significantly after post-weld annealing with the higher post weld annealing temperature resulting in the greatest change. The increase in the ductile-brittle transition temperature for ASTAR-811CN summarized below is illustrated in Figure 5.

DBTT (°F)	1 Hour Post Weld Annealing Temperature (°F)
-225	As-Welded
-200	1800
-100	2200
< 0	2600

TABLE 3 - Ductile-Brittle Transition Temperature of Post (TIG) Weld Annealed NASV-23^(a)
(Ta-7W-1Re-1Hf-0.012C-0.012N)

Post Weld Anneal	Test Temperature (°F) (°C)	No Load Bend Angle (Degrees)	Remarks	DBTT	
				(°F)	(°C)
As-TIG Welded	-250 -157	90	Failure	-225	-143
	-225 -143	91	Bend		
1 Hr. at 980°C 1800°F	-100 -73	92	Bend		
	-200 -129	92	Bend		
	-225 -143	77	Brittle failure in weld		
	-250 -157	44	Brittle failure in weld and HAZ		
	-320 -196	30	Brittle failure in weld and HAZ		
1 Hr. at 1200°C 2200°F	-100 -73	91	Bend	-100	-73
	-125 -87	77	Brittle failure in weld		
	-150 -101	26	Brittle failure in weld and HAZ		
	-200 -129	37	Brittle failure in weld and HAZ		
1 Hr. at 1425°C 2600°F	75 23	92	Bend		
	50 10	90	Very slight ductile failure in weld		
	25 -4	90	Very slight ductile failure in weld		
	0 -18	90	Very slight ductile failure in weld		
	-100 -73	52	Brittle failure in weld and HAZ		
				<0	<-18

(a) Specimens were all annealed for 1 hour at 1650°C (3000°F) prior to welding.

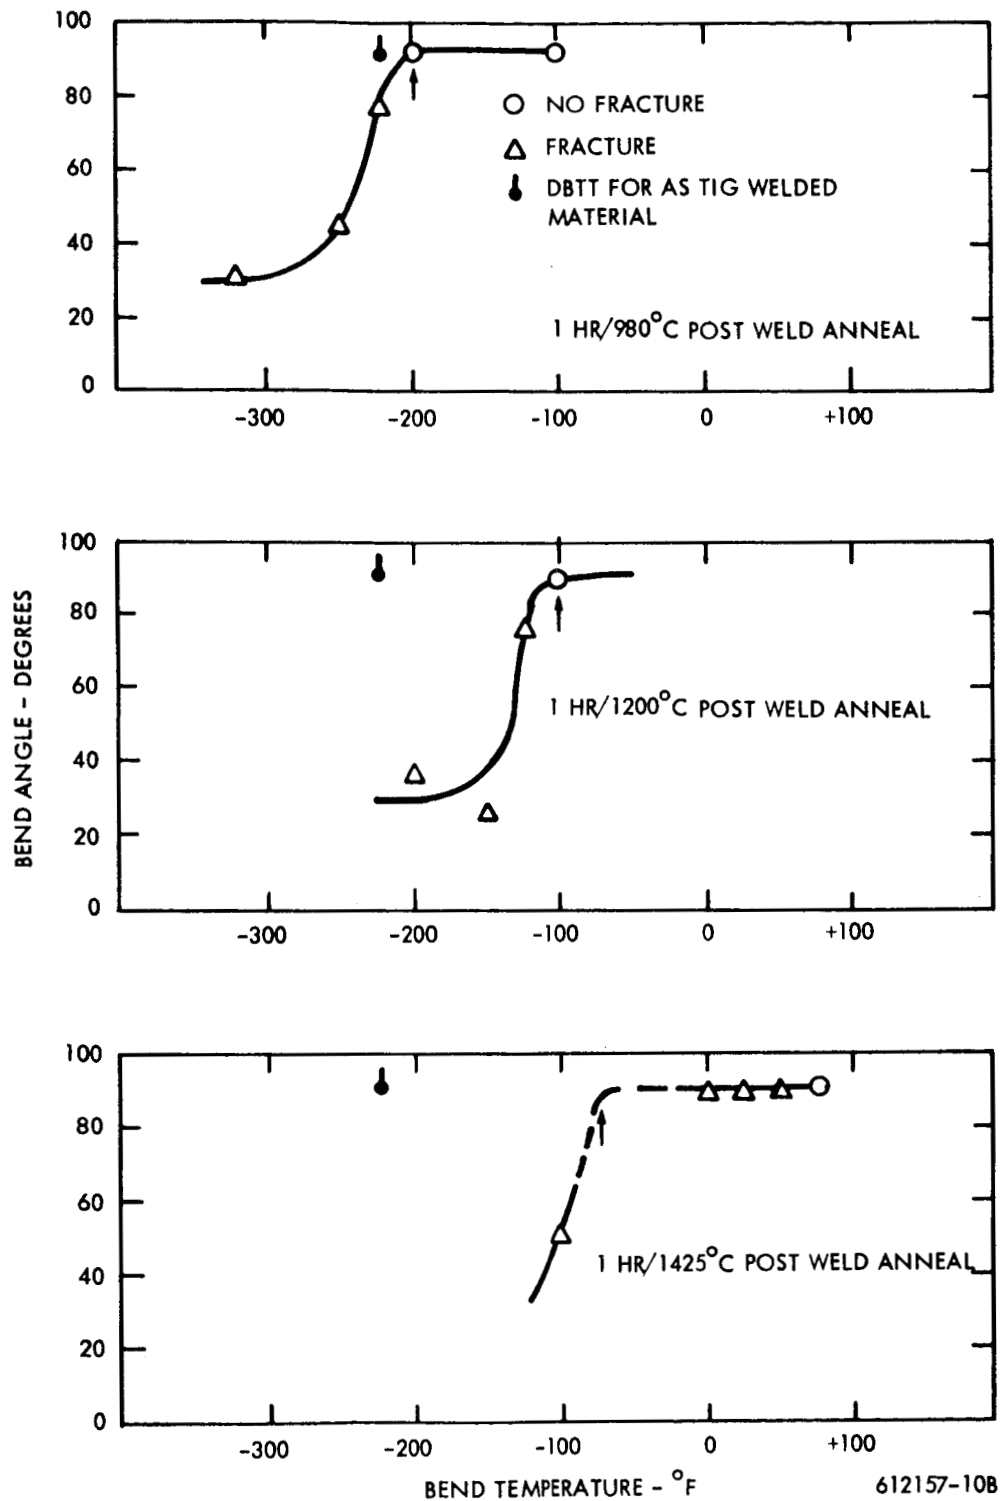


FIGURE 5 - Ductile-Brittle Transition Temperature Test Results for Post (TIG) Weld Annealed ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N)


Failure occurred primarily within the weld and heat affected zones and appeared to be intergranular in nature.

Hardness traverses were made on transverse sections of as-electron beam and as-TIG welded sheet and post-weld annealed specimens of both alloys. The hardness traverses for as-electron beam and as-TIG welded ASTAR-811 and ASTAR-811CN sheet are shown in Figure 6. Little hardness variation was observed in either alloy across the base metal, weld, and heat affected zone. This same behavior was exhibited by the specimens which were post-weld annealed, although there was a decrease in hardness level of from 275 to 255 DPH for the ASTAR-811CN while that of the ASTAR-811 remained essentially unchanged.

The microstructures of the as-TIG welded ASTAR-811 and ASTAR-811CN were essentially single phase in the base metal, fusion, and heat affected zones. The few isolated precipitates observed are assumed to be primarily HfO_2 in the ASTAR-811 and Ta_2C in the ASTAR-811CN. The photomicrographs in Figure 7 are typical of microstructures which were observed for ASTAR-811 and ASTAR-811CN in the as-welded condition.


The microstructure of the as-TIG welded ASTAR-811 remained essentially unchanged after the post weld annealing treatment. An exception however was that a sub-boundary network formed in the heat affected zone and some precipitation occurred near the weld/heat affected zone interface after post weld annealing for 1 hour at 2200°F (see Figure 8). Thus the post weld annealing treatments did not alter the ductile-brittle transition temperature of ASTAR-811 which is consistent with the observed absence of hardness and microstructural changes.

Post weld annealing ASTAR-811CN however did produce significant changes in the as-TIG welded single phase microstructure. The resulting microstructures produced by the 1 hour post weld anneals at 1800, 2200, and 2600°F are shown in Figure 9. Extensive precipitation occurred throughout the base metal, fusion, and heat affected zones during each of the post

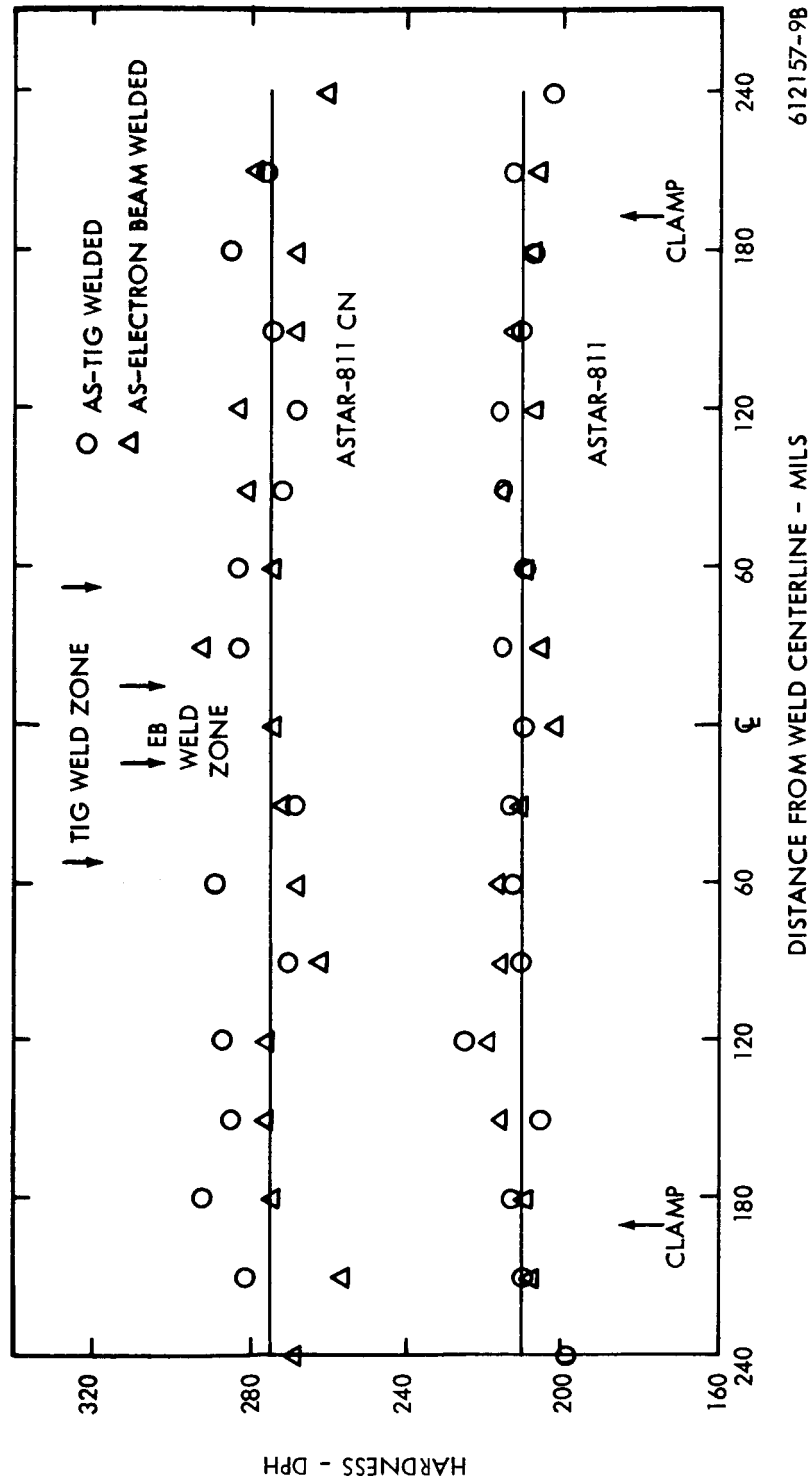


612157-9B


FIGURE 6 - Results of Hardness Traverses Across As-Welded Specimens of ASTAR-811 (Ta-8W-1Re-1Hf) and ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N)

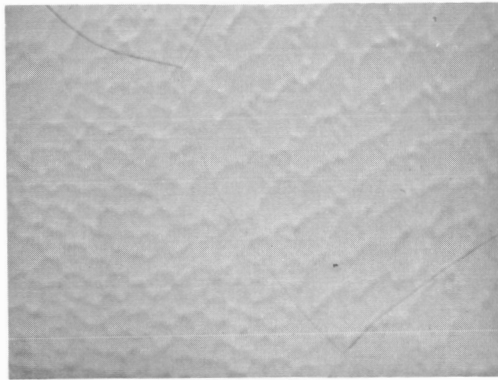

(a) Weld Zone

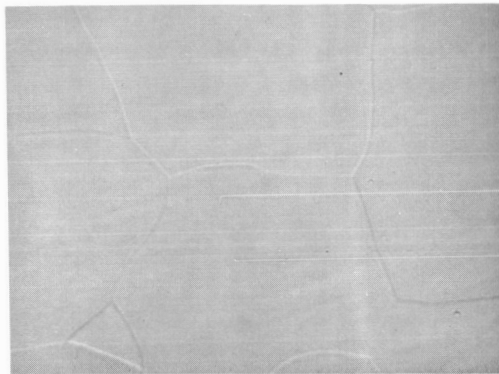

(b) Heat Affected Zone

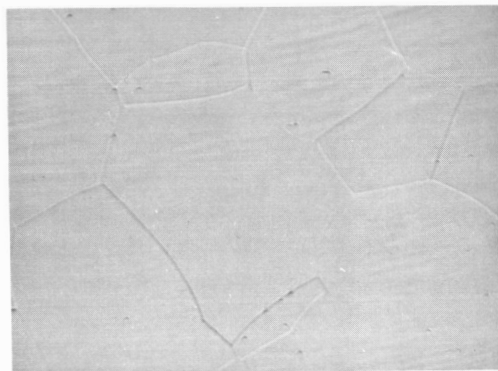


(c) Base Metal

FIGURE 7 - Representative Microstructures of TIG Welded
ASTAR-811 (Ta-8W-1Re-1Hf) 500X




1500X

FIGURE 8 - Microstructure of Weld Zone/Heat Affected Zone Interface in TIG
Welded ASTAR-811 (Ta-8W-1Re-1Hf) Specimen After 1 Hr. Post
Weld Anneal at 1200°C (2200°F)

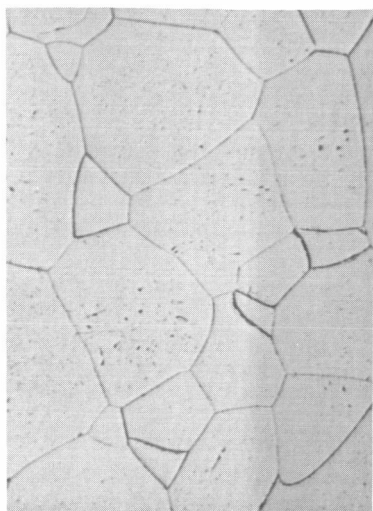


500X

Base Metal

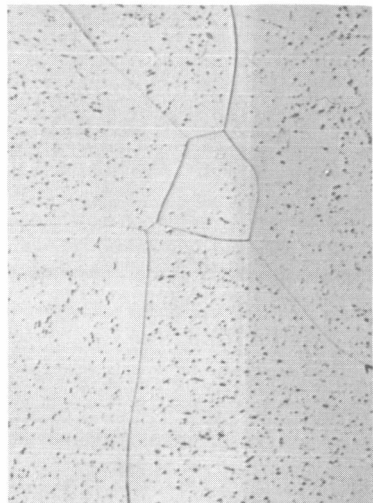

500X


HAZ

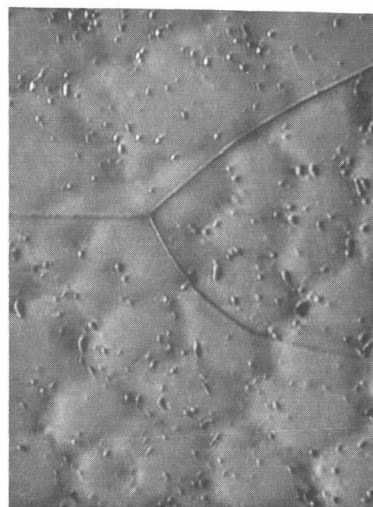

1500X


Weld Zone

Post Weld Annealed for 1 Hour at 980°C (1800°F)

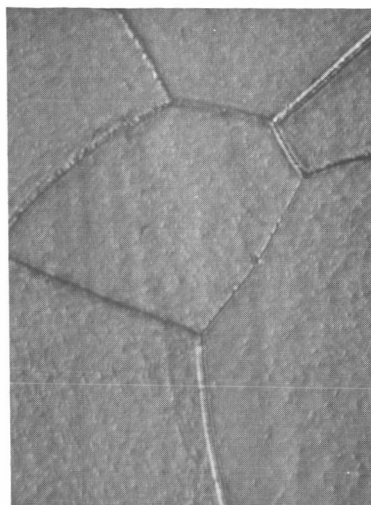


1500X

Base Metal

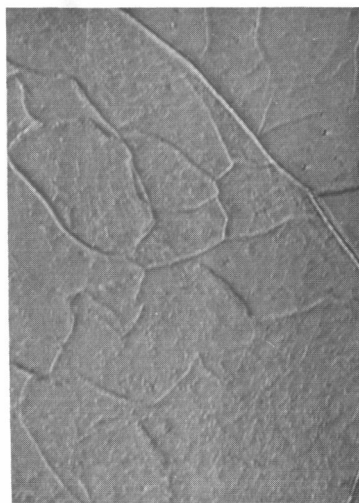

1500X

HAZ

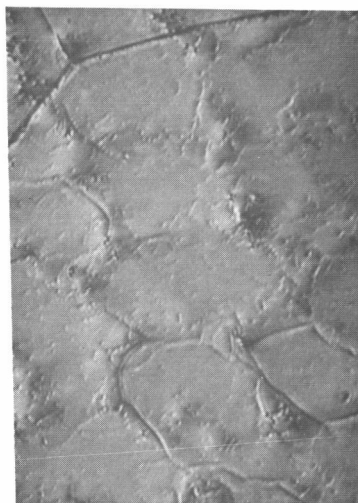


1500X

Weld Zone

Post Weld Annealed for 1 Hour at 1200°C (2200°F)

FIGURE 9 - Microstructures of TIG Welded ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N) Specimens After 1 Hr. Post Weld Anneals at Various Temperatures

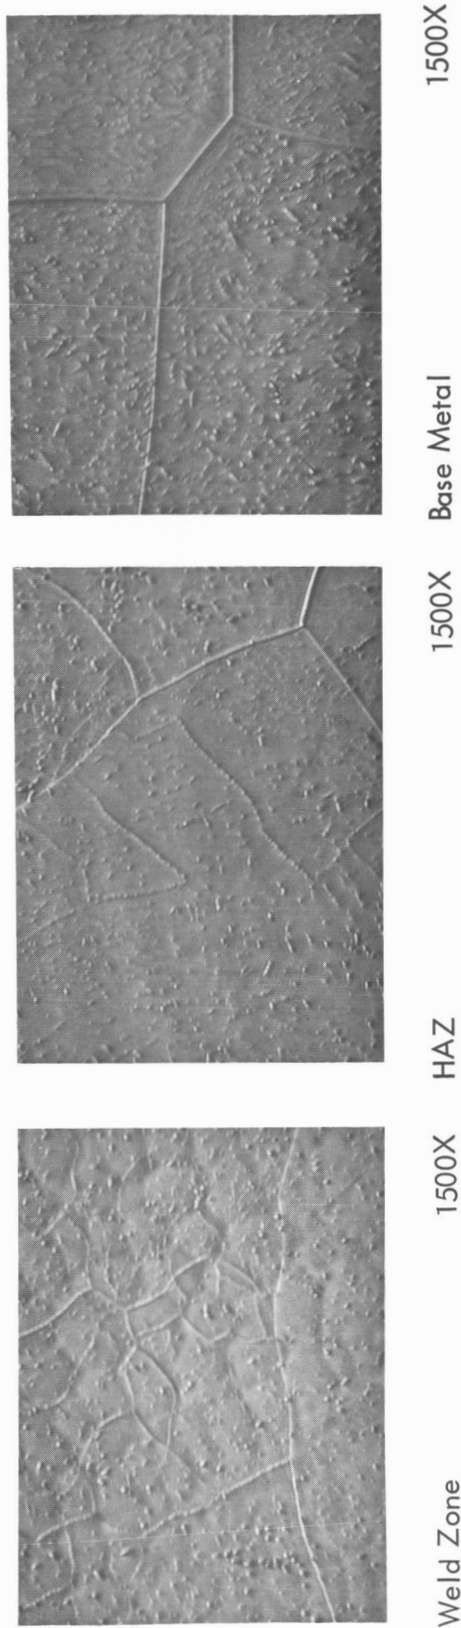

Post Weld Annealed for 1 Hour at 1425°C (2600°F)

FIGURE 9 (continued) - Microstructures of TIG Welded ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N) Specimens After 1 Hr. Post Weld Anneals at Various Temperatures

weld annealing treatments. The formation of this precipitate, which is most likely Ta_2C , no doubt accounts for the observed hardness decrease.

The distribution of the precipitate however did appear to be affected by the annealing temperature. At $1800^{\circ}F$, the precipitation occurred primarily throughout the matrix while at $2200^{\circ}F$ and $2600^{\circ}F$, precipitates were formed at primary grain boundaries and cell and sub-boundaries in the fusion and heat affected zones. The cell and sub-boundary precipitates were larger after annealing at $2600^{\circ}F$. This change in precipitate distribution can thus be used to qualitatively explain the increase in ductile-brittle transition temperature with increasing post weld annealing temperature, particularly as the annealing temperature was increased from 1800 to $2200^{\circ}F$.

D. MECHANICAL PROPERTIES

1. Tensile Properties of TIG Welds — Bead-on-plate tungsten inert gas (TIG) welded specimens of ASTAR-811 and ASTAR-811CN were tested over the temperature range of -320 to $2600^{\circ}F$ (-195 to $1425^{\circ}C$) to evaluate the effects of welding on tensile properties. The welds, both longitudinal and transverse, were made on 0.04-inch thick sheet which had been annealed for 1 hour at $1650^{\circ}C$ ($3000^{\circ}F$) prior to welding. Tensile data are recorded in Table 4A along with the previously obtained data for ASTAR-811C. The tensile data for both ASTAR-811 and ASTAR-811CN appear to be anomalous in that the ductility values at room temperature were lower than those obtained at $-195^{\circ}C$ ($-320^{\circ}F$).

An additional set of room temperature tungsten inert gas (TIG) welded tensile specimens of each alloy were made and retested because of these anomalous results. Sections of 0.33-inch plate, processed from the side forgings, were annealed for 1 hour at $1700^{\circ}C$ ($3090^{\circ}F$) and rolled to 0.05-inch sheet, from which specimen blanks were obtained. These blanks were then annealed for 1 hour at $1650^{\circ}C$ ($3000^{\circ}F$) and the required transverse and longitudinal bead-on-plate TIG welds were made. Specimens, 0.04-inch thick, were machined from the welded blanks, x-rayed to ensure that no weld defects were present, and tested at room

**TABLE 4A - Tensile Properties of TIG Welded ASTAR-811, ASTAR-811C,
and ASTAR-811CN**

Composition and Heat No.	Test Temp. (°F)	Weld Direction	0.2% Yield Strength (ksi)	Ultimate Tensile Strength (ksi)	% Elongation	
					Uniform	Total
ASTAR-811 (Ta-8W-1Re-1Hf) Heat NASV-22	-320	Longitudinal	133.7	157.0	16.3	18.6
	-320	Transverse	137.3	160.6	16.0	19.7
	RT	Longitudinal	77.3	---	8.15	8.3
	RT	Transverse	80.5	---	8.3	8.6
	1800	Longitudinal	36.2	57.6	---	18.1
	2000	Transverse	30.7	47.2	---	10.7
	2400	Longitudinal	27.8	32.2	---	6.6
	2600	Transverse	24.3	28.5	---	4.9
ASTAR-811C (Ta-8W-1Re-0.7Hf- 0.025C) Heat NASV-20	-320	Longitudinal	157.3	184.6	16.7	24.2
	-320	Transverse	159.0	176.2	10.9	14.2
	RT	Longitudinal	109.8	115.3	15.0	28.5
	RT	Transverse	89.3	107.2	10.6	18.7
	1800	Longitudinal	44.0	67.1	---	18.7
	2400	Longitudinal	35.3	41.1	---	29.0
	2600	Longitudinal	32.5	36.0	---	26.7
ASTAR-811CN (Ta-7W-1Re-1Hf- 0.012C-0.012N) Heat NASV-23	-320	Longitudinal	166.4	---	5.25	5.4
	-320	Longitudinal	163.0	194.5	17.4	22.5
	RT	Transverse	106.3	113.5	9.7	11.3
	RT	Transverse	110.8	116.3	9.6	15.4
	1800	Longitudinal	45.3	70.6	---	20.6
	2000	Transverse	40.0	65.0	---	16.4
	2400	Longitudinal	37.2	45.4	---	19.7
	2600	Transverse	31.0	35.9	---	21.5

TABLE 4B - Tensile Properties of TIG Welded ASTAR-811 and ASTAR-811CN

Composition and Heat No.	Test Temperature (°F)	Weld Direction	0.2% Yield Strength (ksi)	Ultimate Tensile Strength (ksi)	% Elongation	
					Uniform	Total
ASTAR-811 (Ta-8W-1Re-1Hf) Heat NASV-22	-320	Longitudinal	134.6	152.3	17.50	22.15
	-320	Transverse	137.0	148.0	11.25	14.35
	RT	Longitudinal	77.6	92.3	14.60	19.15
	RT	Transverse	79.2	90.9	9.20	11.95
ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N) Heat NASV-23	-320	Longitudinal*	162.0	188.0	4.85	5.50
	-320	Transverse*	158.4	189.8	3.70	5.90
	RT	Longitudinal	109.0	116.0	13.15	22.70
	RT	Transverse	110.0	114.0	3.65	5.95

*The stress-strain curves indicated that twinning may have occurred.

temperature and at -320°F . The results are recorded in Table 4B. Where significant differences were noted, they are assumed to represent defective weldments in the original specimens. The test results for the ASTAR-811CN weldments indicate that the fracture mode is changing from ductile to brittle at -320°F .

2. Creep Properties — Creep properties for 0.04-inch thick ASTAR-811 and ASTAR-811CN sheet were obtained at 2200 – 2600°F at stress levels of $8,000$ – $19,000$ psi. The data are recorded in Table 5. These data normalized using the Larson-Miller parameter are plotted in Figure 10 along with data for T-111 and ASTAR-811C. The creep strength of the solid solution composition ASTAR-811 is slightly better than T-111 but significantly inferior to both ASTAR-811C and ASTAR-811CN. The effects of the individual additions on creep strength at 2400°F and $15,000$ psi are summarized below.

Composition w/o	Time to 1% Strain at 2400°F and $15,000$ psi
Ta-8W-2Hf (T-111)	20
Ta-8W-1Re-1Hf (ASTAR-811)	54
Ta-8W-1Re-1Hf-0.025C (ASTAR-811C)	260
Ta-7W-1Re-1Hf-0.012C-0.012N (ASTAR-811CN)	157

Although there is an apparent increase in creep resistance when rhenium is added to the tantalum matrix the increase may be due to the reduction of hafnium content, which has already been shown to exert a pronounced affect on creep strength.⁽¹⁾ There is however no doubt concerning the effect of the carbon and/or nitrogen additions on creep strength. Additional tests are underway to establish the stress and temperature dependence for each composition.


E. PHASE IDENTIFICATION

Information as to the identity of the precipitating phase(s) in the tantalum alloy matrix and their stability as a function of temperature and time is of vital importance.

TABLE 5 - Creep Properties of ASTAR-811 and ASTAR-811CN^(a)

Composition	Test Temperature (°F)	Stress (psi)	Test Duration (hrs.)	Total Elongation (%)	Time to 1% Strain (hrs.)	Vickers Hardness DPH	
						Pre-Test	Post Test
ASTAR-811 (Ta-8W-1Re-1Hf) (Heat NASV-22)	2200	19,000	826	6.4	185	213	212
	2200	15,000	1670	0.66	---	213	209
	2400	15,000	165	4.6	54		
	2400	12,766	377	1.3	317	209	213
ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N) (Heat NASV-23)	2200	19,000	835	2.9	607	294	241
	2400	15,000	426	7.3	157	287	228
	2400	12,500	530	1.43	403	296	228
	2600	8,000	382	5.4	172	290	245

(a) Specimens annealed at 1650°C for 1 hr. at 1×10^{-5} torr then tested at $<1 \times 10^{-8}$ torr.

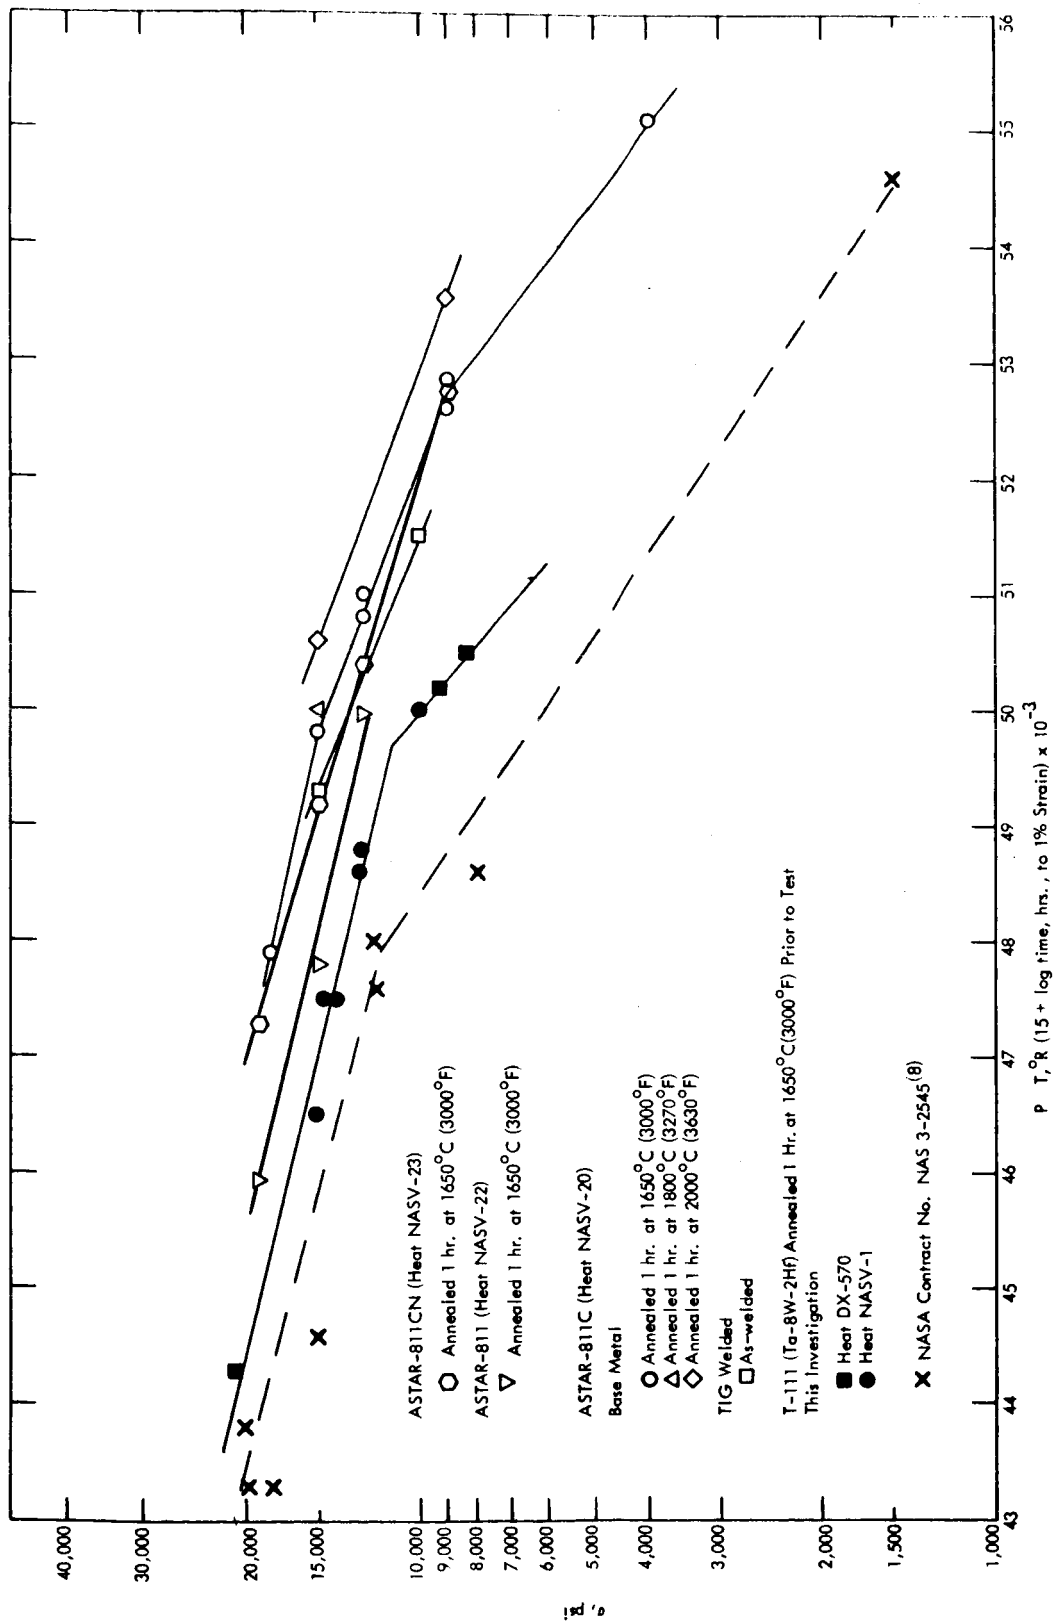

Understanding of these phase relationships will aid in identifying the mechanism(s) contributing to the low and elevated temperature strength thus allowing more precise control over the final mechanical properties.

Prior work on the Ta-8W-1Re-1Hf-0.025C (ASTAR-811C) composition has shown that the dimetal carbide (Ta_2C) is the only precipitating phase. It was also shown that the morphology of the Ta_2C precipitate could be significantly altered by thermal treatment. ⁽⁴⁾

During this period, phase identification work has been carried out on the Ta-7W-1Re-1Hf-0.012C-0.012N composition (ASTAR-811CN). This alloy is essentially identical to ASTAR-811C except one half of the carbon has been replaced with an equivalent amount of nitrogen.

The dispersed phases present in the ASTAR-811CN at the various stages of processing from the as-cast ingot to 0.04 inch sheet were chemically extracted and analyzed by x-ray diffraction. The results which are recorded in Table 6 indicate only the presence of the HCP dimetal carbide Ta_2C ($a_o = 3.10 - 3.11 \text{ \AA}$, $c_o = 4.94 \text{ \AA}$, $c/a = 1.59$). There is however very minor amounts of monoclinic HfO_2 present which no doubt results from the residual oxygen. The amount of Ta_2C which occurred after annealing sheet at 3000°F and above is generally quite small since the carbon solvus for ASTAR-811CN is exceeded at or slightly above this temperature. No evidence of a nitride phase was detected and is consistent with previous work on tantalum alloy compositions containing 100-150 ppm nitrogen. ⁽⁹⁾

Subsequent aging at lower temperatures was carried out over the temperature range of 2000-2600°F for times of 1 and 16 hours on ASTAR-811CN 0.04 inch sheet which had been solution annealed at 3000°F for 1 hour. Longer time aging treatments (up to 1000 hours) over this same temperature range are in progress and will be completed during the next report period. X-ray diffraction results on the residues chemically extracted from these specimens are listed in Table 7. Only Ta_2C was observed after aging for 1 and 16 hours up to 2400°F

**TABLE 6 - X-ray Diffraction Analyses of Various ASTAR-811CN
(Ta-7W-1Re-1Hf-0.012C-0.012N) Bulk Extracted Residues**

Specimen	Phases	Comments
As-cast	HCP Ta ₂ C	1
As-upset forged at 1400°C (2550°F)	HCP Ta ₂ C Mono HfO ₂ (VW)	1
Forged + annealed (1 hr./1650°C (3000°F))	HCP Ta ₂ C Mono HfO ₂ (VW)	1
As-rolled 0.06" sheet	HCP Ta ₂ C	1
0.06" sheet annealed (1 hr./1700°C (3090°F))	HCP Ta ₂ C	1
As-rolled 0.04" sheet	HCP Ta ₂ C Mono HfO ₂ (VW)	1
0.04" sheet annealed (1 hr./1650°C (3000°F))	HCP Ta ₂ C	1

NOTE: Approximate lattice parameters of all the HCP Ta₂C phases were:

$$a_o = 3.10 \text{ to } 3.11 \overset{\circ}{\text{\AA}} \quad c_o = 4.94 \overset{\circ}{\text{\AA}} \quad c/a = 1.59$$

VW - VeryWeak, VVW - Very Very Weak

(1) Diffraction lines partially resolved

TABLE 7 - X-ray Diffraction Analyses of Phases Extracted from ASTAR-811CN (Ta-7W-1Re-1Hf-0.012C-0.012N) Specimens Annealed for 1 Hour at 1650°C and Aged for 1 and 16 Hours at 1090, 1200, 1315, and 1425°C.

Specimen	Phases	Comments
0.04" sheet annealed (1 hr./1650°C (3000°F))	HCP Ta ₂ C	1
+(1 hr./1090°C (2000°F))	HCP Ta ₂ C	1
+(1 hr./1200°C (2200°F))	HCP Ta ₂ C	
+(1 hr./1315°C (2400°F))	HCP Ta ₂ C	
	Mono HfO ₂ (VW)	
+(1 hr./1425°C (2600°F))	HCP Ta ₂ C	1
	Mono HfO ₂ (VW)	
+(16 hrs./1090°C (2000°F))	HCP Ta ₂ C	
+(16 hrs./1200°C (2200°F))	HCP Ta ₂ C	
	Mono HfO ₂ (VW)	
+(16 hrs./1315°C (2400°F))	HCP Ta ₂ C	1
	Mono HfO ₂ (VW)	
+(16 hrs./1425°C (2600°F))	HCP Ta ₂ C (S)	1
	Mono HfO ₂ (VW)	
	FCC Hf(CN) (M)	$a_o = 4.56 \text{ \AA}$

NOTE: Approximate lattice parameters of all the HCP Ta₂C phases were:

$$a_o = 3.10 \text{ to } 3.11 \text{ \AA} \quad c_o = 4.94 \text{ \AA} \quad c/a = 1.59$$

(1) Diffraction lines partially resolved

and after 1 hour at 2600°F. However, after 16 hours at 2600°F, a FCC phase, most likely Hf(CN), is beginning to form. Accompanying the formation of the Ta₂C and Hf(CN) precipitate is a drop in the room temperature hardness (See Figure 11). The largest change in hardness occurred after the first hour which is indicative of the rapid precipitation kinetics of the carbide precipitation reaction. The room temperature hardness after aging for 16 hours at 2000, 2200, and 2400°F is similar. However there is a definite increase in the hardness level for specimens aged at 2600°F which may reflect the higher interstitial solubility or may be related to the nitride precipitation reaction. The appearance of the FCC phase was not unexpected since a similar composition tested early in this investigation exhibited the same behavior.⁽⁹⁾

III. FUTURE WORK

During the next period the following will be accomplished.

1. Initiate creep testing of controlled grain size creep specimens.
2. Continue investigation on the effect of long time annealing treatments on the phase morphology and stability of the ASTAR-811C and ASTAR-811CN.
3. Complete 500 hour annealing treatment at 2200°F on TIG welded ASTAR-811CN (Heat NASV-23) and determine ductile brittle transition temperature.

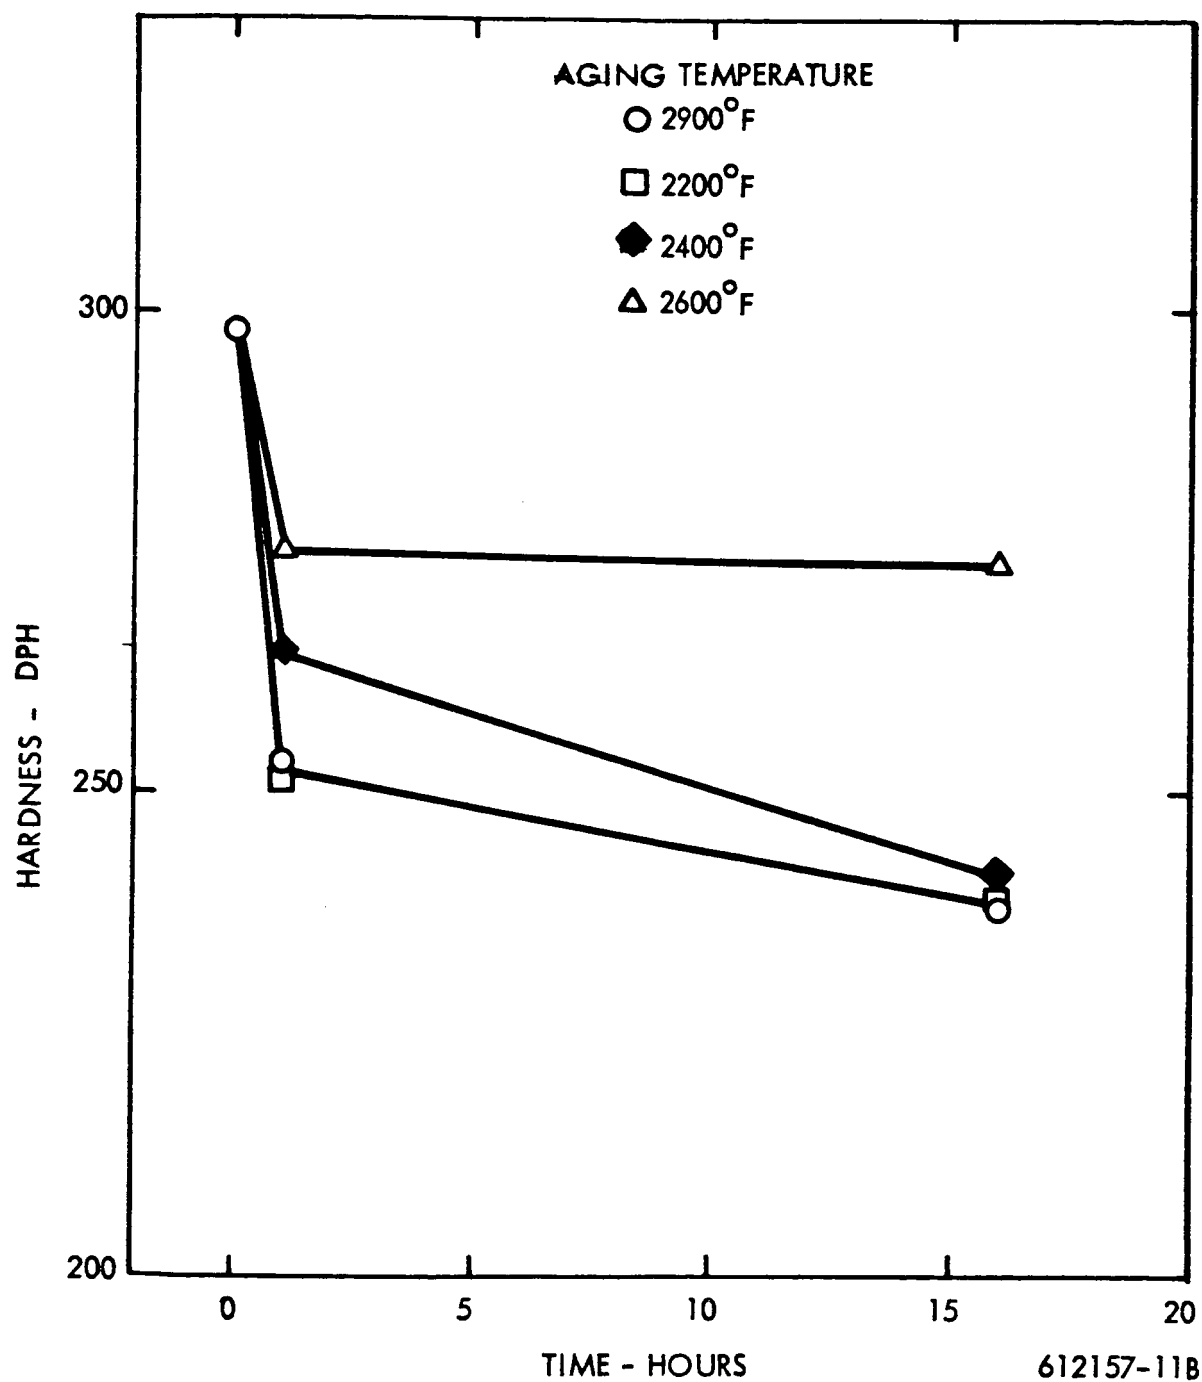


FIGURE 11 - Aging Behavior of ASTAR-811CN
(Annealed 1 Hr. at 3000°F Prior to Aging)

IV. REFERENCES

1. R. W. Buckman, Jr. and R. T. Begley, "Development of Dispersion Strengthened Tantalum Base Alloy", Final Technical Report, Phase I, WANL-PR-(Q)-004.
2. R. W. Buckman, Jr. and R. C. Goodspeed, "Development of Dispersion Strengthened Tantalum Base Alloy", 11th Quarterly Progress Report, WANL-PR(Q)-012, NASA-CR-72094.
3. R. W. Buckman, Jr. and R. C. Goodspeed, "Development of Dispersion Strengthened Tantalum Base Alloy", 12th Quarterly Progress Report, WANL-PR(Q)-013, NASA-CR-
4. R. W. Buckman, Jr. and R. C. Goodspeed, "Development of Dispersion Strengthened Tantalum Base Alloy", 10th Quarterly Progress Report, WANL-PR-(Q)-011, NASA-CR-72093.
5. R. Resnick and L. J. Castleman, 1960 Trans. AIME, 218, 307.
6. R. W. Buckman, Jr., "Development of Dispersion Strengthened Tantalum Base Alloy", 5th Quarterly Progress Report, WANL-PR-(Q)-006, NASA-CR-4462.
7. R. W. Buckman, Jr. and R. T. Begley, "Development of Dispersion Strengthened Tantalum Base Alloy", 3rd Quarterly Progress Report, WANL-PR-(Q)-003, NASA-CR-54105.
8. J. Sawyer and E. A. Steigerwald, "Generation of Long Time Creep Data of Refractory Metal Alloys at Elevated Temperature", 12th Quarterly Report, NAS-CR-72044, NASA Contract 3-2545.
9. R. W. Buckman, Jr. and R. C. Goodspeed, "Development of Dispersion Strengthened Tantalum Base Alloy", 6th Quarterly Progress Report, WANL-PR-(Q)-007, NASA-CR-54658.

DISTRIBUTION LIST

TRW
Caldwell Research Center
23555 Euclid Avenue
Cleveland, Ohio 44117
Attn: Librarian
Attn: G. J. Guarnieri

TRW
New Devices Laboratories
7209 Platt Avenue
Cleveland, Ohio 44104
Attn: Librarian

National Aeronautics & Space Adm.
Washington, D. C. 20546
Attn: Walter C. Scott
Attn: James J. Lynch (RN)
Attn: George C. Deutsch (RR)
Attn: S. V. Manson

National Aeronautics & Space Adm.
Scientific and Technical Inf. Facility
Box 5700
Bethesda, Maryland 21811

NASA-Ames Research Center
Moffet Field, California 94035
Attn: Librarian

NASA-Goddard Space Flight Center
Greenbelt, Maryland 20771
Attn: Librarian

NASA-Langley Research Center
Hampton, Virginia 23365
Attn: Librarian

NASA-Manned Spacecraft Center
Houston, Texas 77001
Attn: Librarian

NASA-Jet Propulsion Laboratory
4800 Oak Grove Drive
Pasadena, California 91103
Attn: Librarian

NASA-Lewis Research Center
21000 Brookpark Road
Cleveland, Ohio 44135
Attn: Librarian
Attn: Dr. Bernard Lubarsky
Attn: Mr. R. L. Cummings
Attn: Mr. G. M. Ault
Attn: Mr. J. Joyce
Attn: Mr. P. E. Moorhead
Attn: Mr. N. T. Musial
Attn: Mr. T. Strom
Attn: Mr. T. A. Moss
Attn: Dr. Louis Rosenblum
Attn: J. Creagh
Attn: Mr. J. Dilley
Attn: Mr. J. J. Fackler
Attn: Mr. I. I. Pinkel
Attn: Mr. G. Tuliak
Attn: Mr. W. D. Klopp
Attn: Mr. C. Hoffman
Attn: NASA-Lewis Lab. Report Central
Section

NASA- Western Operations Office
150 Pico Boulevard
Santa Monica, California 90406
Attn: Mr. John Keeler

National Bureau of Standards
Washington 25, D. C.
Attn: Librarian

NASA-George C. Marshall Space Flight Center
Huntsville, Alabama 35812
Attn: Librarian
Attn: Wm. A. Wilson

Aeronautical Systems Division
Wright-Patterson Air Force Base, Ohio
Attn: Charles Armbruster
Attn: T. Cooper
Attn: Librarian
Attn: John L. Morris
Attn: H. J. Middendorp
Attn: G. Thompson
Attn: G. Sherman

Army Ordnance Frankford Arsenal
Bridesburg Station
Philadelphia 37, Pennsylvania
Attn: Librarian

Bureau of Ships
Dept. of the Navy
Washington 25, D. C.
Attn: Librarian

Bureau of Weapons
Research and Engineering
Material Division
Washington 25, D. C.
Attn: Librarian

U. S. Atomic Energy Commission
Technical Reports Library
Washington 25, D. C.
Attn: J. M. O'Leary

U. S. Atomic Energy Commission
Germantown, Maryland
Attn: Col. E. L. Douthett
Attn: H. Rothen
Attn: Major Gordon Dicker

U. S. Atomic Energy Commission
Technical Information Service Extension
P. O. Box 62
Oak Ridge, Tennessee

U. S. Atomic Energy Commission
Washington 25, D. C.
Attn: M. J. Whitman

Argonne National Laboratory
9700 South Cross Avenue
Argonne, Illinois
Attn: Librarian

Brookhaven National Laboratory
Upton, Long Island, New York
Attn: Librarian

Oak Ridge National Laboratory
Oak Ridge, Tennessee
Attn: W. O. Harms
Attn: Dr. A. J. Miller
Attn: Librarian
Attn: N. T. Bray

Office of Naval Research
Power Division
Washington 25, D. C.
Attn: Librarian

U. S. Naval Research Laboratory
Washington 25, D. C.
Attn: Librarian

Advanced Technology Laboratories
Division of American Standard
369 Whisman Road
Mountain View, California
Attn: Librarian

Aerojet General Corporation
P. O. Box 296
Azusa, California
Attn: Librarian

Aerojet General Nucleonics
P. O. Box 77
San Ramon, California
Attn: Librarian

AiResearch Manufacturing Company
Sky Harbor Airport
402 South 36th Street
Phoenix, Arizona
Attn: Librarian
Attn: E. A. Kovacevich

AiResearch Manufacturing Company
9851-9951 Sepulveda Boulevard
Los Angeles 45, California
Attn: Librarian

I. I. T. Research Institute
10 W. 35th Street
Chicago, Illinois 60616

Atomics International
8900 DeSoto Avenue
Canoga Park, California 91304
Attn: W. Botts

Avco
Research & Advanced Development Dept.
201 Lowell Street
Wilmington, Massachusetts
Attn: Librarian

Babcock and Wilcox Company
Research Center
Alliance, Ohio
Attn: Librarian

Battelle Memorial Institute
505 King Avenue
Columbus, Ohio
Attn: C. M. Allen
Attn: Librarian
Attn: Defense Metals Inf. Center

The Bendix Corporation
Research Laboratories Division
Southfield, Detroit 1, Michigan
Attn: Librarian

Bell Aerosystems Co.
P. O. Box 1
Buffalo 5, New York
Attn: E. J. King

The Boeing Company
Seattle, Washington
Attn: Librarian

Brush Beryllium Company
17876 St. Clair Avenue
Cleveland, Ohio 44110
Attn: Librarian

Carborundum Company
Niagara Falls, New York
Attn: Librarian

Chance Vought Aircraft Inc.
P. O. Box 5907
Dallas 22, Texas
Attn: Librarian

Clevite Corporation
Mechanical Research Division
540 East 105th Street
Cleveland 8, Ohio
Attn: Mr. N. C. Beerli

Climax Molybdenum Company of Michigan
1600 Huron Parkway
Ann Arbor, Michigan
Attn: Librarian

Convair Astronautics
50001 Kerny Villa Road
San Diego 11, California
Attn: Librarian

E. I. duPont deNemours and Co., Inc.
Wilmington 98, Delaware
Attn: Librarian

Electro-Optical Systems, Inc.
Advanced Power Systems Division
Pasadena, California
Attn: Librarian

Fansteel Metallurgical, Corp.
North Chicago, Illinois
Attn: Librarian

Ford Motor Company
Aeronutronics
Newport Beach, California
Attn: Librarian

General Dynamics/General Atomic
P. O. Box 608
San Diego, California 92112
Attn: Librarian

General Electric Company
Atomic Power Equipment Div.
P. O. Box 1131
San Jose, California

General Electric Company
Flight Propulsion Laboratory Dept.
Cincinnati 15, Ohio
Attn: Librarian
Attn: Dr. J.W. Semmel

General Electric Company
Missile and Space Vehicle Dept.
3198 Chestnut Street
Philadelphia 4, Pennsylvania
Attn: Librarian

General Electric Company
Vallecitos
Vallecitos Atomic Lab.
Pleasanton, California
Attn: Librarian

Herring Corp.
7356 Greenback Drive
Hollywood, California 91605
Attn: Don Adams

General Dynamics/Fort Worth
P. O. Box 748
Fort Worth, Texas
Attn: Librarian

General Motors Corporation
Allison Division
Indianapolis 6, Indiana
Attn: Librarian

Hamilton Standard
Div. of United Aircraft Corp.
Windsor Locks, Connecticut
Attn: Librarian

Hughes Aircraft Company
Engineering Division
Culver City, California
Attn: Librarian

Lockheed Missiles and Space Div.
Lockheed Aircraft Corp.
Sunnyvale, California
Attn: Librarian

Marquardt Aircraft Co.
P. O. Box 2013
Van Nuys, California
Attn: Librarian

The Martin Company
Baltimore 3, Maryland
Attn: Librarian

The Martin Company
Nuclear Division
P. O. Box 5042
Baltimore 20, Maryland
Attn: Librarian

Martin Marietta Corp.
Metals Technology Laboratory
Wheeling, Illinois

Massachusetts Institute of Technology
Cambridge 39, Massachusetts
Attn: Librarian



Materials Research and Development
Manlabs Inc.
21 Erie Street
Cambridge 39, Massachusetts

Materials Research Corporation
Orangeburg, New York
Attn: Librarian

McDonnell Aircraft
St. Louis, Missouri
Attn: Librarian

MSA Research Corporation
Callery, Pennsylvania
Attn: Librarian

North American Aviation
Los Angeles Division
Los Angeles 9, California
Attn: Librarian

National Research Corp.
Metals Division
45 Industrial Place
Newton, Massachusetts 02164
Attn: Dr. M. L. Torte
Director of Metallurgical Research

Lawrence Radiation Laboratory
Livermore, California
Attn: Dr. James Hadley
Head, Reactor Division

Pratt & Whitney Aircraft
400 Main Street
East Hartford 8, Connecticut
Attn: Librarian

Republic Aviation Corporation
Farmingdale, Long Island, New York
Attn: Librarian

Solar
2200 Pacific Highway
San Diego 12, California

Southwest Research Institute
8500 Culebra Road
San Antonio 6, Texas
Attn: Librarian

Rocketdyne
Canoga Park, California
Attn: Librarian

Superior Tube Co.
Norristown, Pennsylvania
Attn: Mr. A. Bound

Sylvania Electric Products, Inc.
Chem. & Metallurgical
Towanda, Pennsylvania
Attn: Librarian

Temescal Metallurgical
Berkeley, California
Attn: Librarian

Union Carbide Stellite Corp.
Kokomo, Indiana
Attn: Librarian

Union Carbide Metals
Niagara Falls, New York
Attn: Librarian

Union Carbide Nuclear Company
P. O. Box X
Oak Ridge, Tennessee
Attn: X-10 Laboratory Records Department

United Nuclear Corporation
Research & Engineering Center
Grassland Road
Elmsford, New York 10523
Attn: Librarian
Attn: Mr. Albert Weinstein



Astronuclear
Laboratory

Universal Cyclops Steel Corp.
Refractomet Division
Bridgeville, Pennsylvania
Attn: C. P. Mueller

TRW Space Technology Laboratories
One Space Park
Redondo Beach, California
Attn: Librarian

University of California
Lawrence Radiation Lab.
P. O. Box 808
Livermore, California
Attn: Librarian

University of Michigan
Department of Chemical & Metallurgical Eng.
Ann Arbor, Michigan
Attn: Librarian

Vought Astronautics
P. O. Box 5907
Dallas 22, Texas
Attn: Librarian

Wolverine Tube Division
Calumet & Hecla, Inc.
17200 Southfield Road
Allen Park, Michigan
Attn: R. C. Cash

Wyman-Gordon Co.
North Grafton, Massachusetts
Attn: Librarian

Wah Chang Corporation
Albany, Oregon
Attn: Librarian

Lawrence Radiation Laboratory
P. O. Box 808
Livermore, California 94551
Attn: Richard R. Vandervoort